RELIABILITY TEST DATA

Safety Standard Certified Lead Type Disc Ceramic Capacitors for General Purpose

MURATA PN : DE1E3RA472M***Q01F Type RA

Rated Voltage(Y1) : AC500V(r.m.s.)/DC1500V

PAGE

INNOVATOR IN ELECTRONICS


2. ROBUSTNESS of TERMINATIONS	2
3. SOLDERABILITY of LEADS	2
4. SOLDERING EFFECT	3
5. HUMIDITY (UNDER STEADY STATE)	4
6. HUMIDITY LOADING (AC)	5
7. HUMIDITY LOADING (DC)	6
8. LIFE (AC)	7
9. LIFE (DC)	8
10. FLAME TEST	9
11. ACTIVE FLAMMABILITY	10
12. PASSIVE FLAMMABILITY	11
13. TEMPERATURE CYCLE	12
	muRa

1. TEMPERATURE CHARACTERISTIC

Condition : 1.0 kHz, 1.0 V(r.m.s.)


Specification : +20 / -55% (Temp. Range : -25 to 85 °C, Reference Temp. : 20 °C)

Sample Qty. : 5 pcs.

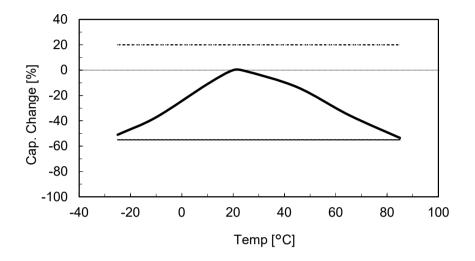

2. ROBUSTNESS of TERMINATIONS

Condition : < TENSILE > Fix the body of capacitor,and apply a tensile weight gradually to each lead wire in the radial direction of capacitor up to 10 N and keep it for 10 s.



< BENDING > Each lead wire shall be subjected to 5 N weight and then a 90° bend, at the point of egress, in one direction return to original position, and then a 90° bend in the opposite direction at the rate of one bend in 2 to 3 s.

Specification : Lead wire should not cut off. Capacitor should not be broken.

Result

:

No.	TENSILE	BENDING
1	OK	OK
2	OK	OK
3	OK	OK
4	OK	OK
5	OK	OK
6	OK	OK
7	OK	OK
8	OK	OK
9	OK	OK
10	OK	OK

3. SOLDERABILITY of LEADS

- Condition : The lead wire of a capacitor should be dipped into a ethanol solution of 25wt% rosin and then into molten solder (Sn-3Ag-0.5Cu) of 245 °C for 2 s.
- Specification : Lead wires should be soldered with uniformly coated on the axial direction over 3/4 of the circumferential direction.
- Sample Qty. : 10 pcs.


No.	RESULT
1	OK
2	OK
3	OK
4	OK
5	OK
6	OK
7	OK
8	OK
9	ОК ОК ОК ОК ОК ОК ОК ОК
10	OK

4. SOLDERING EFFECT

< Non-preheat >

Condition	: Solder temp. Immersion time	350 °C 3.5 s
	Pre-treatment	Store at 125 °C for 1 h, and apply the AC4000V(r.m.s.) 60s, then place at room condition for 24 h.
	Post-treatment	Place at room condition for 1 to 2 h.

Sample Qty. : 10 pcs.

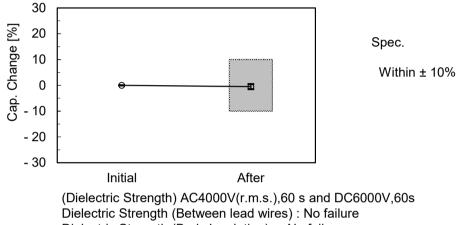


Dielectric Strength (Between lead wires) : No failure Dielectric Strength (Body Insulation) : No failure Insulation Resistance (I.R.) : $1000M\Omega$ min. Appearance : No marked defect

<On-preheat >


Condition	: Pre-heat Solder temp. Immersion time	120 °C, 60 s 260 °C 7.5 s
	Pre-treatment	Store at 125 °C for 1 h, and apply the AC4000V(r.m.s.) 60s, then place at room condition for 24 h.
	Post-treatment	Place at room condition for 1 to 2 h.

Sample Qty. : 10 pcs.

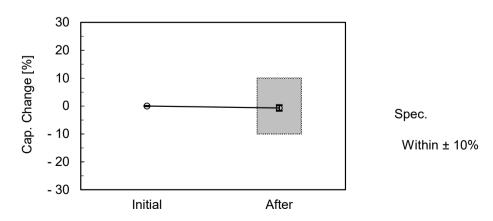


(Dielectric Strength) AC4000V(r.m.s.),60 s and DC6000V,60s Dielectric Strength (Between lead wires) : No failure Dielectric Strength (Body Insulation) : No failure Insulation Resistance (I.R.) : $1000M \Omega$ min. Appearance : No marked defect


5. HUMIDITY (UNDER STEADY STATE)

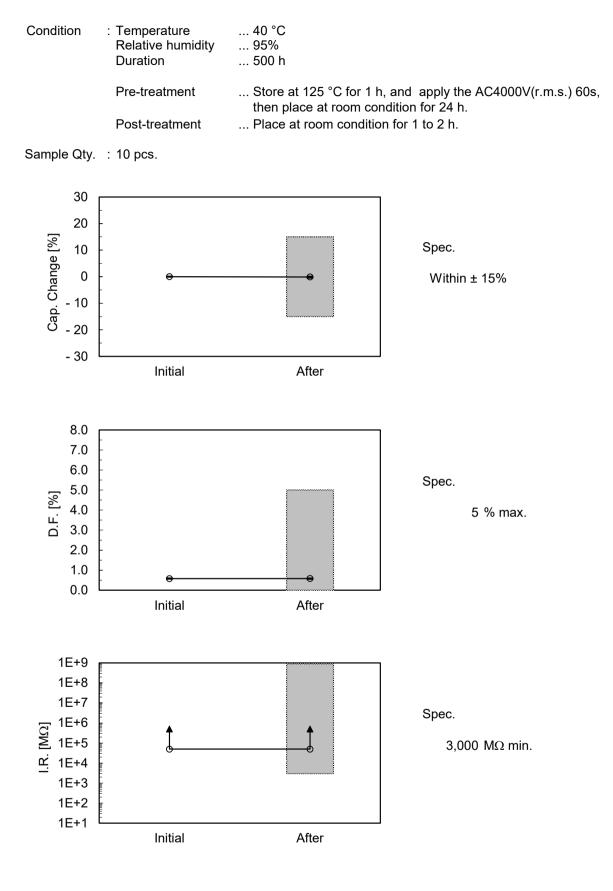

6. HUMIDITY LOADING (AC)

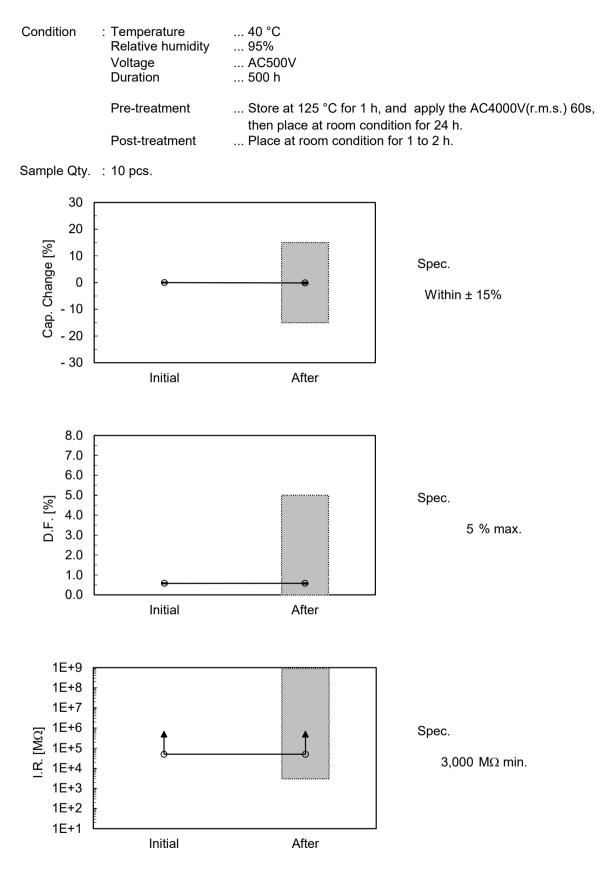


7. HUMIDITY LOADING (DC)

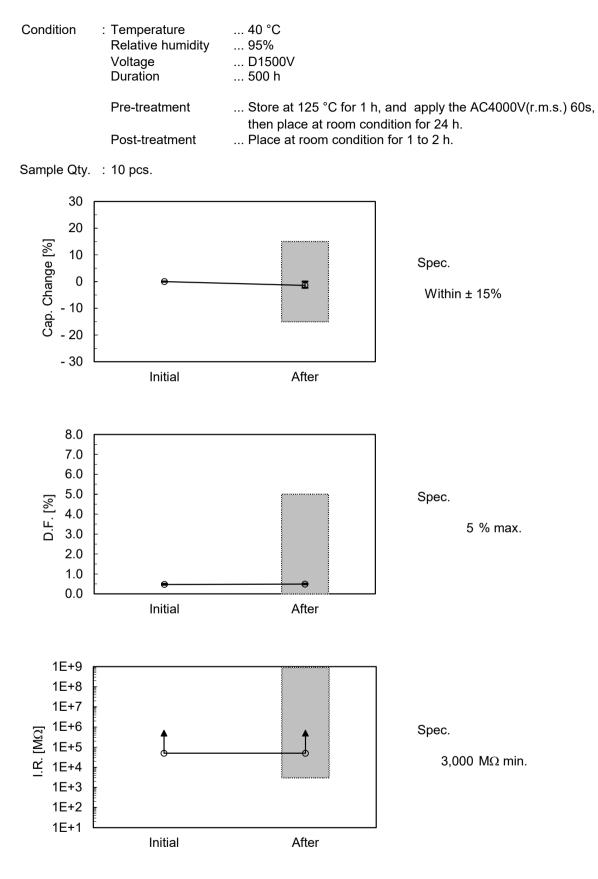

8. LIFE (AC)


Condition	: Temperature Voltage	125°C AC 850 V(r.m.s.) [Once each hour the voltage is increased to AC 1,000 V(r.m.s.) for 0.1 s.]
	Duration	1,000 h
	Before-life test	Each individual capacitor shall be subjected to a 12 kV impulses.
	Pre-treatment	Store at 125 °C for 1 h, and apply the AC4000V(r.m.s.) 60s, then place at room condition for 24 h.
	Post-treatment	Place at room condition for 24 h.

Sample Qty. : 10 pcs.

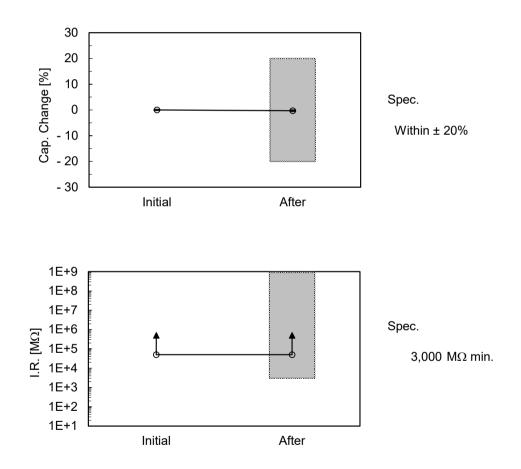


9. LIFE (DC)

Condition	: Temperature Voltage Duration	125°C DC2550V 1,000 h
	Before-life test	Each individual capacitor shall be subjected to a 12 kV impulses.
	Pre-treatment	Store at 125 °C for 1 h, and apply the AC4000V(r.m.s.) 60s, then place at room condition for 24 h.
	Post-treatment	Place at room condition for 24 h.
Sample Qty.	: 10 pcs.	

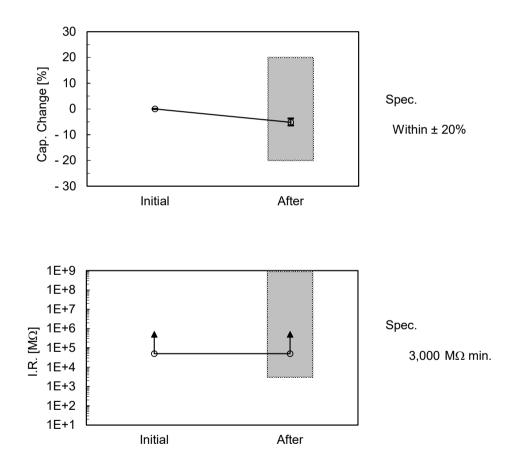

10. FLAME TEST

Condition : The capacitor shall be subjected to applied flame for 15 s, and then removed for 15 s until 5 cycles.

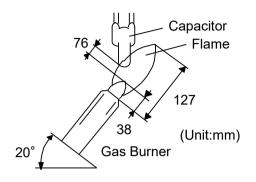

Sample Qty. : 10 pcs.

Specification : The capacitor flame discontinue as follows.

Cycle	Time
1 - 4	30 s max.
5	60 s max.

Result

: No.	Result
1	OK
2	OK
3	OK
4	OK
5	OK
6	OK
7	OK
8	OK
9	OK
10	OK

Osciloscope


Ut


11. ACTIVE FLAMMABILITY

Condition

 The capacitors shall be individually wrapped in at least one but more than two complete layers of cheese-cloth. The capacitor shall be subjected to 20 discharges. The interval between successive discharges shall be 5 s. The U_{AC} shall be maintained for 2 min after the last discharge.

F L1 L2 R **S1** CX C1 C2= C3 -Ct UAC L3 **S**2 L4 Tr ÷

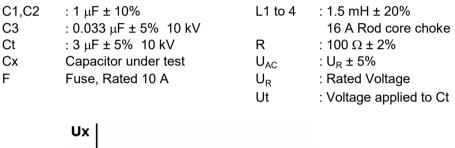

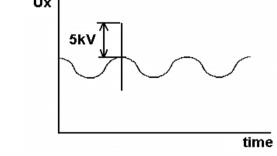


Sample Qty. : 10 pcs.

Specification : The cheese-cloth shall not be on fire.

No.	RESULT
1	OK
2	OK OK
3	OK
4	ОК
5	OK OK
6	OK
7	OK
8	ОК
9	OK
10	OK

12. PASSIVE FLAMMABILITY

Condition : The capacitor under test shall be held in the flame in the position which best promotes burning. Each Specimen shall only be exposed once to the flame. Time of exposure to flame : 30 s.

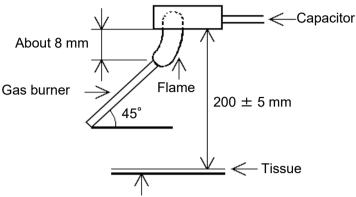

About 10 mm thick board

Length of flame: $12 \pm 1 \text{ mm}$ Gas burner: Length 35 mm min.Inside Dia.: $0.5 \pm 0.1 \text{ mm}$ Outside Dia.: 0.9 mm max.Gas: Butane gas Purity 95% min.

Sample Qty. : 10 pcs.

Specification : The burning time shall not be exceeded the time 30 s. The tissue paper shall not ignite.

No.	RESULT
1	OK
2	OK
3	OK
4	OK
5	OK
6	OK
7	OK
8	OK
9	OK
10	OK

13. TEMPERATURE CYCLE

Condition : The capacitor shall be subjected to 500 temperature cycles.

< Temperature cycle / Cycle time : 500 cycles>

Step	1	2	3	4
Temp.[°C]	-40	Room Temp.	125	Room Temp.
Time[min]	30	3	30	3

Pre-treatment ... Store at 125 °C for 1 h, and apply the AC4000V(r.m.s.) 60s, then place at room condition for 24 h.

Post-treatment ... Place at room condition for 24 h.

Sample Qty. : 10 pcs.

