TYPICAL

RELIABILITY TEST DATA

Safety Standard Certified Lead Type Disc Ceramic Capacitors for General Purpose

MURATA PN: DE2E3KY472M***M01F

	PAGE
1. INITIAL (Cap., D.F. , I.R. ,Dielectric Strength)	1
2. TEMPERATURE CHARACTERISTIC	2
3. ROBUSTNESS of TERMINATIONS	2
4. SOLDERABILITY of LEADS	3
5. SOLDERING EFFECT	4
6. HUMIDITY (UNDER STEADY STATE)	5
7. HUMIDITY LOADING	6
8. LIFE (HIGH TEMPERATURE LOADING)	7
9. FLAME TEST	8
0. ACTIVE FLAMMABILITY	9
1. PASSIVE FLAMMABILITY	10
2. TEMPERATURE & IMMERSION CYCLE	11



1. INITIAL (Cap., D.F., I.R.)


Condition : (Cap., D.F.) 1.0 kHz, 1.0 V(r.m.s.)

(I.R.) DC 500 V, 60 s

(Temp.) 20 °C

(Dielectric Strength) AC2000V(r.m.s.),60 s...(Between lead wires) (Dielectric Strength) AC2600V(r.m.s.),60 s...(Body Insulation)

Sample Qty. : 30 pcs.

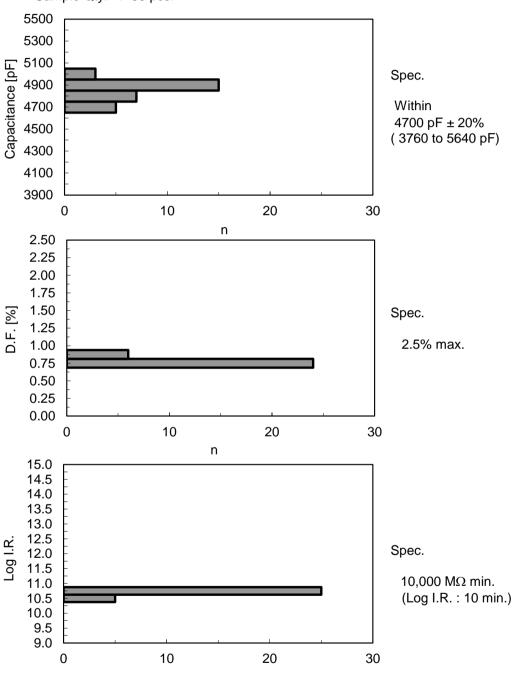

Dielectric Strength (Between lead wires): No failure Dielectric Strength (Body Insulation): No failure

Appearance: No marked defect

Room Condition

Temperature: between 15 to 35 ° C

Relative humidity: between 45 to 75 %


Atm. pressure: between 86 to 106 kPa

2. TEMPERATURE CHARACTERISTIC

Condition: 1.0 kHz, 1.0 V(r.m.s.)

Specification: +20 / -55% (Temp. Range: -25 to 85 °C, Reference Temp.: 20 °C)


Sample Qty. : 5 pcs.

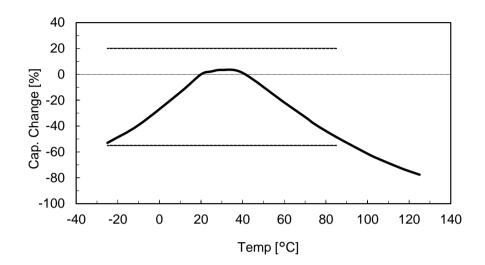

3. ROBUSTNESS of TERMINATIONS

Condition : < TENSILE >

Fix the body of capacitor, and apply a tensile weight gradually to each lead wire in the radial direction of capacitor up to 10 N and keep it for 10 s.



< BENDING >

Each lead wire shall be subjected to 5 N weight and then a 90° bend, at the point of egress,in one direction return to original position,and then a 90° bend in the opposite direction at the rate of one bend in 2 to 3 s.

Specification: Lead wire shall not cut off.

Capacitor shall not be broken.

Result

:			BENDING
	1	OK	OK
	2	OK	OK
	3	OK	OK
	4	OK	OK
	5	OK	OK
	6	OK	OK
	7	OK	OK
	8	OK	OK
	9	OK	OK
	10	OK	OK

4.SOLDERABILITY of LEADS

Condition : The lead wires of a capacitor shall be dipped into flux and

then into molten solder (Sn-3Ag-0.5Cu: 245°C, H63A: 235 °C) for 2 s.

Specification: Lead wires shall be soldered with uniformly coated on the

axial direction over 75% of the circumferential direction.

Sample Qty. : 10 pcs.

	RESULT		
No.	Sn-3.0Ag-0.5Cu : 245°C	H63A : 235°C	
1	OK	OK	
2	OK	OK	
3	OK	OK	
4	OK	OK	
5	OK	OK	
6	OK	OK	
7	OK	OK	
8	OK	OK	
9	OK	OK	
10	OK	OK	

5. SOLDERING EFFECT

< Non-Preheat >


Condition : Solder temp. ... 260 °C

Immersion time ... 10 s

Pre-treatment ... Store at 85 °C for 1 h, and then, place at room condition for 24 h.

Post-treatment ... Place at room condition for 1 to 2 h.

Sample Qty. : 10 pcs.

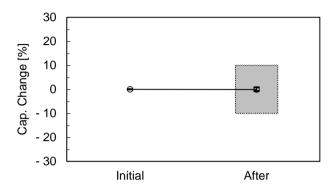

Dielectric Strength

Between lead wires (AC2000V(r.m.s.),60 s): No failure Body Insulation (AC2600V(r.m.s.),60 s): No failure

Insulation Resistance (I.R.): $1000M\Omega$ min.

Appearance: No marked defect

< On-Preheat >


Condition : Preheat ... 120 °C , 60s

Solder temp. ... 260 °C Immersion time ... 7.5 s

Pre-treatment ... Store at 85 °C for 1 h, and then, place at room condition for 24 h.

Post-treatment ... Place at room condition for 1 to 2 h.

Sample Qty. : 10 pcs.

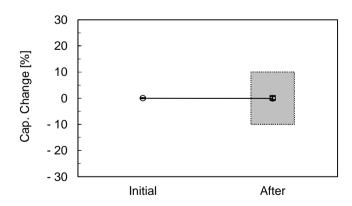

Dielectric Strength

Between lead wires (AC2000V(r.m.s.),60 s): No failure Body Insulation (AC2600V(r.m.s.),60 s): No failure

Insulation Resistance (I.R.): $1000M\Omega$ min.


6. HUMIDITY (UNDER STEADY STATE)

Condition : Temperature ... 40 °C

Relative humidity ... 95% Duration ... 500 h


Post-treatment ... Place at room condition for 1 to 2 h.

Sample Qty. : 10 pcs.

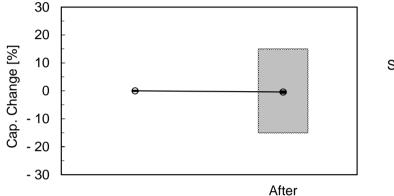


Spec.

Within ± 15%

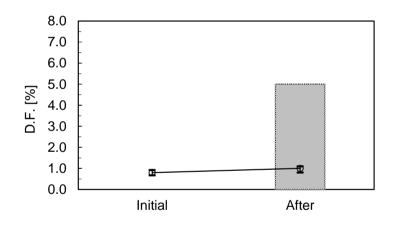

Spec.

5 % max.

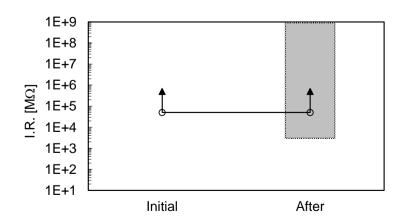

Spec.

3,000 M Ω min.

Dielectric Strength

Between lead wires (AC2000V(r.m.s.),60 s): No failure Body Insulation (AC2600V(r.m.s.),60 s): No failure

7. HUMIDITY LOADING

Condition : Temperature ... 40 °C


Relative humidity ... 95%

Voltage ... Rated Voltage

Duration ... 500 h


Post-treatment ... Place at room condition for 1 to 2 h.

Sample Qty. : 10 pcs.

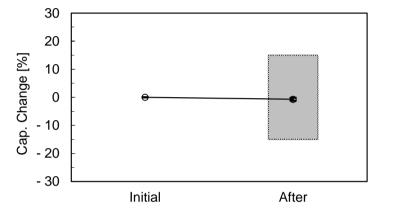


Spec.

Within ± 15%

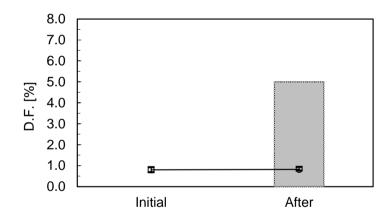

Spec.

5 % max.

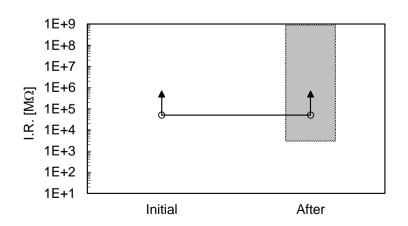

Spec.

3,000 M Ω min.

Dielectric Strength

Between lead wires (AC2000V(r.m.s.),60 s): No failure Body Insulation (AC2600V(r.m.s.),60 s): No failure

8. LIFE (HIGH TEMPERATURE LOADING)

Condition : Temperature ... 125°C

Voltage ... AC 425 V(r.m.s.) [Once each hour the voltage is

increased to AC 1,000 V(r.m.s.) for 0.1 s.]


Duration ... 1,000 h


Pre-treatment ... Each individual capacitor shall be subjected to

a 5 kV impulses.

Post-treatment ... Place at room condition for 1 to 2 h.

Sample Qty. : 10 pcs.

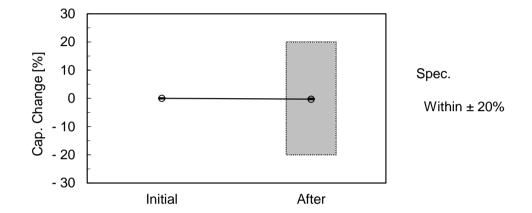

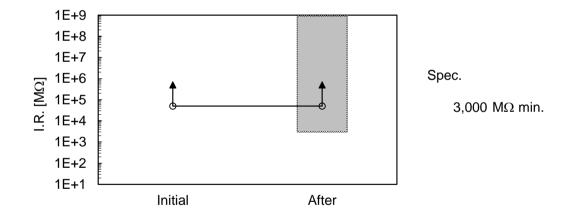


Dielectric Strength

Between lead wires (AC2000V(r.m.s.),60 s) : No failure Body Insulation (AC2600V(r.m.s.),60 s) : No failure

9. FLAME TEST

Condition : The capacitor shall be subjected to applied flame for 15 s, and then removed for 15 s until 5 cycles.

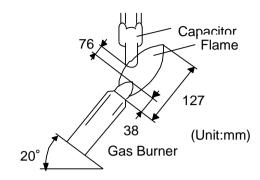

Sample Qty. : 10 pcs.

Specification: The capacitor flame discontinue as follows.

Cycle	Time
1 - 4	30 s max.
5	60 s max.


No.	Result
1	OK
2	OK
3	OK OK
4	OK
5	OK
6	OK
7	OK
8	OK
9	OK OK
10	OK

10. ACTIVE FLAMMABILITY

Condition

: The capacitors shall be individually wrapped in at least one but more than two complete layers of cheese-cloth. The capacitor shall be subjected to 20 discharges. The interval between successive discharges shall be 5 s.


The U_{AC} shall be maintained for 2 min after the last discharge.

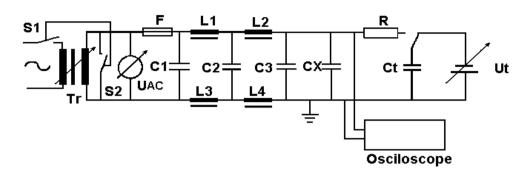

C1,C2 : 1 μ F ± 10% L1 to L4 : 1.5 mH ± 20%

C3 : $0.033 \,\mu\text{F} \pm 5\% \,\, 10 \,\, \text{kV}$ 16 A Rod core choke

Ut : Voltage applied to Ct

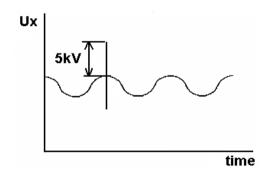

Sample Qty. : 10 pcs.


Specification: The cheese-cloth shall not be on fire.

No.	RESULT
1	OK
2	OK
3	OK
4	OK
5	OK
6	OK
7	OK
8	OK
9	OK
10	OK

11. PASSIVE FLAMMABILITY

Condition

: The capacitor under test shall be held in the flame in the position which best promotes burning. Each Specimen shall only be exposed once to the flame. Time of exposure to flame : 30 s.

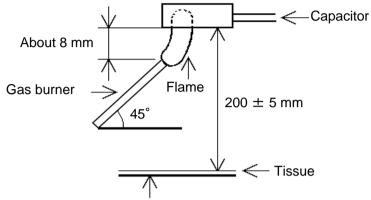

About 10 mm thick board

Length of flame : $12 \pm 1 \text{ mm}$

Gas burner : Length 35 mm min.

Inside Dia. : 0.5 ± 0.1 mm Outside Dia. : 0.9 mm max.

Gas : Butane gas Purity 95% min.

Sample Qty. : 10 pcs.

Specification: The burning time shall not be exceeded the time 30 s.

The tissue paper shall not ignite.

No.	RESULT
1	OK
2	OK
3	OK
4	OK
5	OK
6	OK
7	OK
8	OK
9	OK
10	OK

12. TEMPERATURE & IMMERSION CYCLE

Condition

: The capacitor shall be subjected to 5 temperature cycles, then consecutively to 2 immersion cycles.

< Temperature cycle / Cycle time : 5 cycles>

Step	1	2	3	4
Temp.[°C]	-40	Room Temp.	125	Room Temp.
Time[min]	30	3	30	3


< Immersion cycle / Cycle time : 2 cycles>


Step	Temp.[°C]	Time[min]	Immersion water
1	65	15	Clean water
2	0	15	Saturated salt water


Pre-treatment ... Store at 85 °C for 1 h, and then, place at room condition for 24 h.

Post-treatment ... Place at room condition for 24 h.

Sample Qty. : 10 pcs.

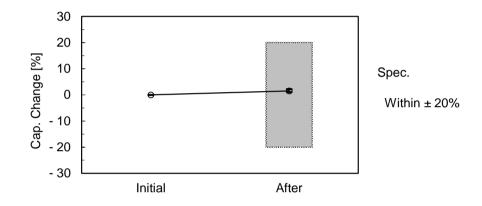

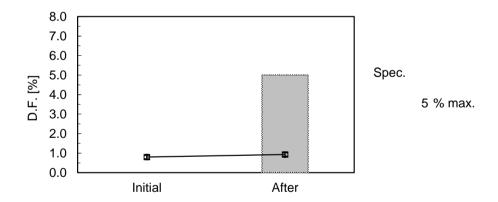

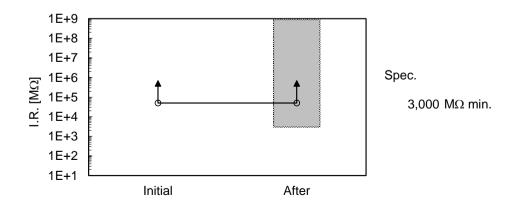

Dielectric Strength

Between lead wires (AC2000V(r.m.s.),60 s): No failure Body Insulation (AC2600V(r.m.s.),60 s): No failure